

AD-A178 339


FOCUSED ION BEAM FABRICATION OF GRADED CHANNEL FET'S  
(FIELD EFFECT TRANSI (U) MASSACHUSETTS INST OF TECH  
CAMBRIDGE RESEARCH LAB OF ELECTRON J J MELNGAILIS  
MAR 87 MDA903-85-C-0215 F/G 9/1

1/1

UNCLASSIFIED

NL



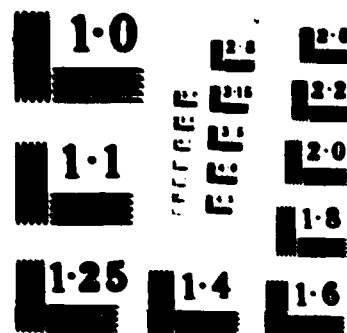

AD-A178 339

Focused Ion Beam Fabrication  
of Graded Channel FET's  
in GaAs and Si

Semiannual Technical Report  
1 July 1986 - 31 December 1986

by John Melngailis  
DARPA/DOD Contract  
MDA 903-85-C-0215

DTIC  
ELECTE  
MAR 25 1987  
S D

Massachusetts Institute of Technology  
Research Laboratory of Electronics  
Cambridge, MA 02139

DTIC FILE COPY

DISTRIBUTION STATEMENT A  
Approved for public release;  
Distribution Unlimited

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE

A5-2-11-1

## REPORT DOCUMENTATION PAGE

1a. REPORT SECURITY CLASSIFICATION			1b. RESTRICTIVE MARKINGS		
2a. SECURITY CLASSIFICATION AUTHORITY			3. DISTRIBUTION/AVAILABILITY OF REPORT Approved for public release; distribution unlimited		
2b. DECLASSIFICATION/DOWNGRADING SCHEDULE					
4. PERFORMING ORGANIZATION REPORT NUMBER(S)			5. MONITORING ORGANIZATION REPORT NUMBER(S)		
6a. NAME OF PERFORMING ORGANIZATION Research Laboratory of Electronics Massachusetts Institute of Technology		6b. OFFICE SYMBOL (If applicable)	7a. NAME OF MONITORING ORGANIZATION Department of the Navy Naval Electronic Systems Command		
6c. ADDRESS (City, State and ZIP Code) 77 Massachusetts Avenue Cambridge, MA 02139			7b. ADDRESS (City, State and ZIP Code) Washington, D.C. 20363 - 5100		
8a. NAME OF FUNDING/SPONSORING ORGANIZATION Advanced Res. Projects Agency		8b. OFFICE SYMBOL (If applicable)	9. PROCUREMENT INSTRUMENT IDENTIFICATION NUMBER MDA 903-85-C-0215		
8c. ADDRESS (City, State and ZIP Code)			10. SOURCE OF FUNDING NOS.		
			PROGRAM ELEMENT NO.	PROJECT NO. 1001/1053	TASK NO.
11. TITLE (Include Security Classification) Focused Ion Beam Fabrication of Graded Channel FET's in GaAs and Si					
12. PERSONAL AUTHOR(S) John J. Melngailis					
13a. TYPE OF REPORT Semiann. Tech. Rep.		13b. TIME COVERED FROM 7/1/86 TO 12/31/86		14. DATE OF REPORT (Yr. Mo. Day) March 1987	
15. PAGE COUNT 8					
16. SUPPLEMENTARY NOTATION					
17. COSATI CODES			18. SUBJECT TERMS (Continue on reverse if necessary and identify by block number)		
FIELD	GROUP	SUB. GR.			
19. ABSTRACT (Continue on reverse if necessary and identify by block number)					
Work by J. J. Melngailis and his collaborators is summarized here.					
20. DISTRIBUTION/AVAILABILITY OF ABSTRACT UNCLASSIFIED/UNLIMITED <input checked="" type="checkbox"/> SAME AS RPT. <input type="checkbox"/> DTIC USERS <input type="checkbox"/>			21. ABSTRACT SECURITY CLASSIFICATION Unclassified		
22a. NAME OF RESPONSIBLE INDIVIDUAL Kyra M. Hall RLE Contract Reports			22b. TELEPHONE NUMBER (Include Area Code) (617) 253-2569		22c. OFFICE SYMBOL

**"Focused Ion Beam Fabrication of Graded Channel  
Field Effect Transistors in GaAs and Si"**

**Background**

The aim of this program is to fabricate field effect transistors in Si and GaAs in which the doping in the channel is varied as a function of distance from source to drain. The focused ion beam machine is a unique tool which is capable of producing such graded implants. In achieving this goal alignment procedures of the focused ion beam to existing features on the wafer have to be developed, and the focused ion beam implants must be characterized and compared to conventional implants. In addition, models of the behavior of the graded channel devices must be developed.

**Personnel working on the program:**

Jarvis B. Jacob, Grad. student, Elect. Eng. & Comp. Science  
Henri Lezec, Grad. student, Elect. Eng. & Comp. Science  
Christian Musil, Grad. student, Physics  
Khalid Ismail, Grad. student, Elect. Eng. & Comp. Science  
Len Mahoney, Lincoln Laboratory  
Dimitri Antoniadis, Associate Professor of E.E.&C.S., Coprincipal Investigator  
John Melngailis, Principal Research Scientist, R.L.E., Principal Investigator

**Progress During the Third Half Year Period**

During this period our work has concentrated on refining the techniques for producing focused ion beam implants aligned to existing features, fabricating and testing GaAs FET's with focused ion beam implanted channels, performing test implants in Si, and modeling the behavior of devices with graded doses in the channel.



Availability Codes	
Dist	Avail and/or Special
A-1	

## 1. Implantation Technology Development

We have worked in collaboration with the manufacturer of our focused ion beam machine, IBS, on developing and refining techniques of implanting dopants in areas aligned to existing features and on measuring the minimum beam diameter achieved. The main vehicle for the refining of the techniques was the implantation into GaAs FET's of ions of  $\text{Si}^+$  and  $\text{Si}^{++}$  emitted from an AuSi source. The first implantations relied heavily on the precision laser controlled table and were done essentially using "manual" alignment. Existing features were first located in crosshairs in the middle of the field of view, and their exact position measured with the laser interferometer. Then the location of the feature to be implanted was calculated in this laser table coordinate system. The stage was then moved to this location and the feature was implanted. Since some of the features were bigger than a single field, the implants had to be stitched together. This again was done manually. Based partly on this experience software was written by IBS to do this tedious procedure automatically.

In addition the final octopole of the column has been realigned, and the performance of the ion column has been improved. Beam diameter of near  $0.1 \mu\text{m}$  has been achieved. This is shown in Fig. 1. The ion beam was blanked and stepped from point to point on PMMA. After development the dots are seen to be of less than  $0.1 \mu\text{m}$  diameter, Fig. 1. The machine has had a history now of many weeks of trouble free operation. It has been dismantled and will be moved to M.I.T. on March 13, 1987.

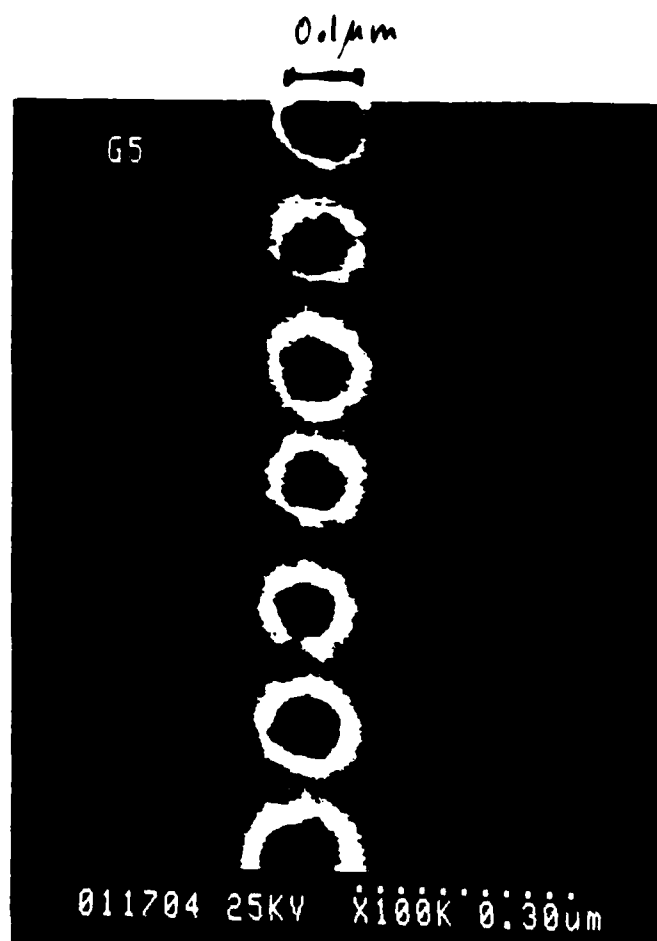


Fig. 1. Focused ion beam exposed. PMMA  $\text{Si}^{++}$  ions at 130 kV (or 260 keV) were used. The PMMA was 0.5  $\mu\text{m}$  thick and was developed in MIBK. The scale marker (row of dots lower right) is 0.3  $\mu\text{m}$ . Thus the exposed dots are less than 0.1  $\mu\text{m}$  diameter.

## 2. GaAs FET's:


The GaAs FET's with focused ion beam implanted channel regions have been tested. Both DC characteristics were measured, and high frequency performance was examined. About 30 devices were implanted with eight different doping gradients, as well as with uniform density implants for control purposes.

The DC characteristics of the graded channel MESFET's showed clear asymmetry, i.e. if source and drain are interchanged, the behavior is quite different as shown in Fig. 2. In the forward direction (drain region more highly doped) the devices showed very flat saturation characteristics while in the reverse direction the saturation region has a positive slope and a curved section. In general, graded devices operated in the forward direction had a transconductance about 20% higher than uniformly doped devices. These results are still quite preliminary. More tests will be carried out.


Five devices were installed in special mounts for high frequency testing, including a control device which had no gradient of doping. Four devices showed gain up to 18 GHz including the control device. One of the devices with a doping gradient showed gain only up to 7.5 GHz and is thought to be defective. One of the devices with a gradient was also tested backwards i.e. with <sup>drain</sup> ~~source~~ grounded. The gain dropped below unity at 13.5 GHz. Thus there is some indication that the doping gradient affects the maximum frequency of operation.

Based on this experience, plans have been made for future work both at 1  $\mu\text{m}$  gate lengths and at gate lengths approaching 0.1  $\mu\text{m}$ . In the latter case self aligned processing must be used; i.e. the graded channel implant



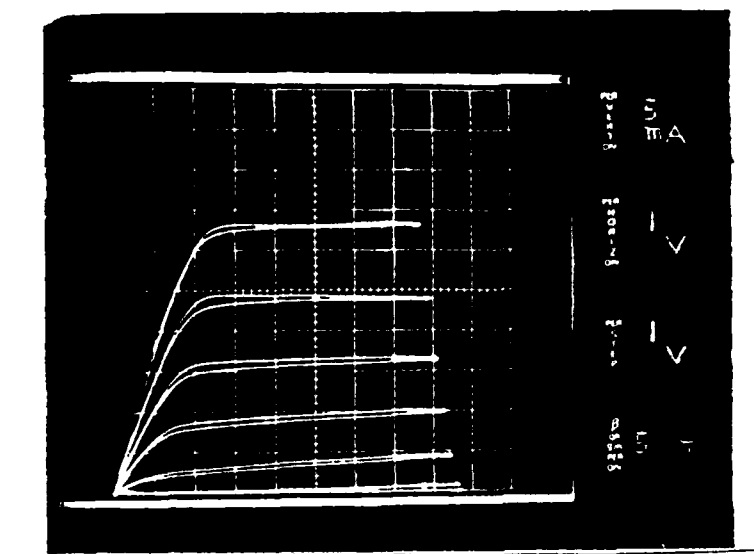

(a)

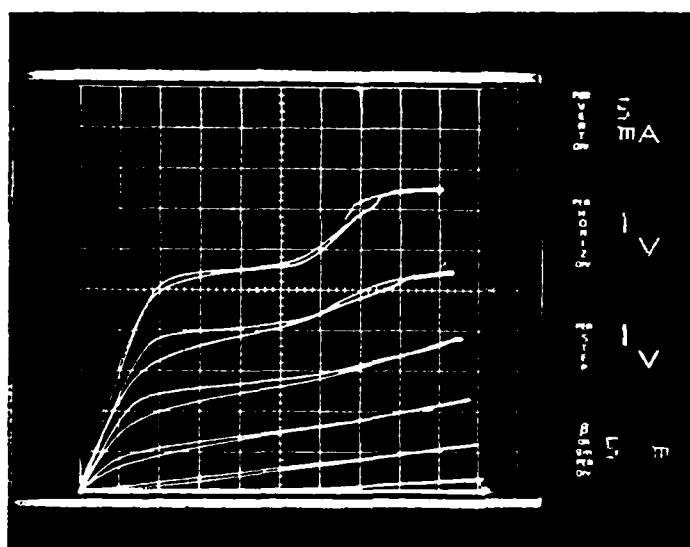

(b)

Fig. 2 Characteristics of laterally graded MESFET on GaAs. The background channel doping dose is  $4.6 \times 10^{12}$  Si ions/cm<sup>2</sup>. The gradient corresponds to a 15% increase in doping across the  $1\mu\text{m}$  gate length from source to drain.

a) Source grounded, drain voltage positive.

b) Drain grounded, source positive.

Vertical scale 5 mA/cm, horizontal 1 V/cm, top trace corresponds to 0V. gate bias, next trace -1V etc. to -6V. gate bias when device is turned off.

and the gate electrode placement must be defined in the same step. A bi-level PMMA resist scheme is used for this purpose. This procedure, as well as other planned experiments and methods of analysis are described in the Ph.D. thesis proposal of Henri Lezec (available upon request).

### 3. Implantation into Si

Test structures are ready for implantation of As and B into Si for the purpose of verifying self-annealing effects due to focused ion beam implantation reported in the literature. Limited implants were carried out with As ions from a Pd/B/As source. Those will be continued when sources become available.

In order to test the distribution of implanted species in the wafer,  $\text{Ga}^+$  ions were implanted at 130 kV at a density of  $10^{15}$  ions/cm<sup>2</sup>. The distribution of the Ga will be measured by SIMS techniques combined with wafer thinning. Since, as mentioned above, some differences in focused-ion-beam implanted and conventionally implanted silicon has been observed, such differences need to be explored before devices are fabricated.

A mask set is being fabricated which will be used for focused ion beam implantation of graded profiles into the channels of MOS transistors. The mask pattern originally designed on the M.I.T. campus using the HPEDIT program was converted to Manplot format appropriate for fabricating the mask at Lincoln Laboratory.

### 4. Device modelling

A simple model has been developed for a MESFET with a channel doping that varies from source to drain under the gate. The device is described as a series of voltage controlled resistors. In each "resistor" the channel height is determined by the gate potential and the channel voltage in that

segment. Values of the transconductance, gate capacitance, and cut-off frequency are deduced at the onset of saturation. The model provides a description of the fundamental causes of performance degradation, even though it neglects such effects as two dimensional current flow and velocity overshoot. It is useful for devices above 1  $\mu\text{m}$  in gate length. This model predicts that the introduction of an appropriate doping gradient under the gate will lead to improvements in the magnitude of transconductance and cutoff frequency and in the linearity of their dependence on gate voltage. Further modeling and experimental verification will be carried out.

## DISTRIBUTION LIST

Director Defense Advanced Research Project Agency 1400 Wilson Boulevard Arlington, Virginia 22209 Attn: Program Management	(3)
Naval Electronic Systems Command Department of the Navy Washington, D. C. 20363	(2)
Administrative Contracting Officer Room E19-628 Massachusetts Institute of Technology Cambridge, Massachusetts 02139	(1)
Director Defense Advanced Research Project Agency Attn: TIO/Admin 1400 Wilson Boulevard Arlington, Virginia 22209	(1)
Defense Technical Information Center Bldg. 5, Cameron Station Alexandria, Virginia 22314	(12)
Director Naval Research Laboratory Attn: Code 2627 Washington, D. C. 20375	(6)
TACTEC Battelle Memorial Institute 505 King Avenue Columbus Ohio 43201	(1)

END

4-87

DTIC